

Anisotropic effect of field on the orthorhombic-to-tetragonal transition in the striped cuprate $(\text{La}, \text{Nd})_{2-x}\text{Sr}_x\text{CuO}_4$.

Z.A. Xu^{1,*}, N. P. Ong¹, T. Noda², H. Eisaki² and S. Uchida²

¹Joseph Henry Laboratories of Physics, Princeton University, Princeton, New Jersey 08544

²School of Frontier Sciences, University of Tokyo, Yayoi 2-11-16, Bunkyo-ku, Tokyo 113-8656, Japan
(February 1, 2008)

The Nd-doped cuprate $\text{La}_{2-y-x}\text{Nd}_y\text{Sr}_x\text{CuO}_4$ displays a first-order phase transition at T_d ($= 74$ K for $x=0.10$, $y = 0.60$) to a low-temperature tetragonal (LTT) phase. A magnetic field $\mathbf{H}$ applied $\parallel$ the a -axis leads to an *increase* in T_d , whereas T_d is decreased when $\mathbf{H} \parallel \mathbf{c}$. These effects show that magnetic ordering involving both Nd and Cu spins plays a key role in driving the LTO-LTT transition. Related anisotropic effects are observed in the uniform susceptibility and the in-plane magnetoresistance.

The observation of static charge and spin modulation in the Nd-doped cuprate $\text{La}_{2-x-y}\text{Nd}_y\text{Sr}_x\text{CuO}_4$ [1,2] has stimulated considerable interest in stripe formation in underdoped cuprates. The compound $\text{La}_{1.6-x}\text{Nd}_{0.4}\text{Sr}_x\text{CuO}_4$ with $x = 0.12$ undergoes an orthorhombic to tetragonal (LTO-LTT) transition at $T_d = 74$ K. Tranquada *et al.* [1] recently observed weak, static charge and spin modulations which appear at temperatures below T_d . The modulation periods are close to ϵ and 2ϵ for the charge and spin stripes, respectively, with $\epsilon \sim x$. The charge modulation has also been observed by hard x -ray scattering in samples with Sr content $x = 0.12$ [3] and 0.15 [4]. Transport measurements reveal that the c -axis resistivity ρ_c increases rapidly at T_d , whereas the Hall coefficient decreases monotonically to a value near zero, implying quasi-one dimensional transport [5,6]. The close similarities between the static stripe structure and the inelastic peaks observed in Nd-free $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ (LSCO) suggest that weak charge ordering may be a general feature of the cuprate phase diagram [7]. Evidence for charged-stripe phase in LSCO (for $0.07 < x < 0.12$) was recently derived from the collapse of the NQR (nuclear quadrupole resonance intensity [8]. Underlying the strong interest in stripes is the proposal that they are responsible for superconductivity in the cuprates [10].

We report an unusual effect of a magnetic field on T_d that highlights the intrinsically magnetic nature of the LTO-LTT transition. An in-plane field $\mathbf{H} \parallel \mathbf{a}$ leads to an increase in T_d while a field $\mathbf{H} \parallel \mathbf{c}$ decreases T_d . The T dependence of the uniform susceptibility and in-plane magnetoresistance are also different, depending on the direction of the field.

I. EXPERIMENTAL

To resolve the MR signal to a few parts per million (ppm), we have calibrated of the field-sensitivity of the regulating thermometer (Lake Shore Cryogenics cernox sensor). A previous calibration (obtained by allowing

the He bath to equilibrate under open-loop control) [11] determined that $\Delta\rho/\rho B^2 = -1.7$ and -2.7 ppm, at 100 and 70 K, respectively.

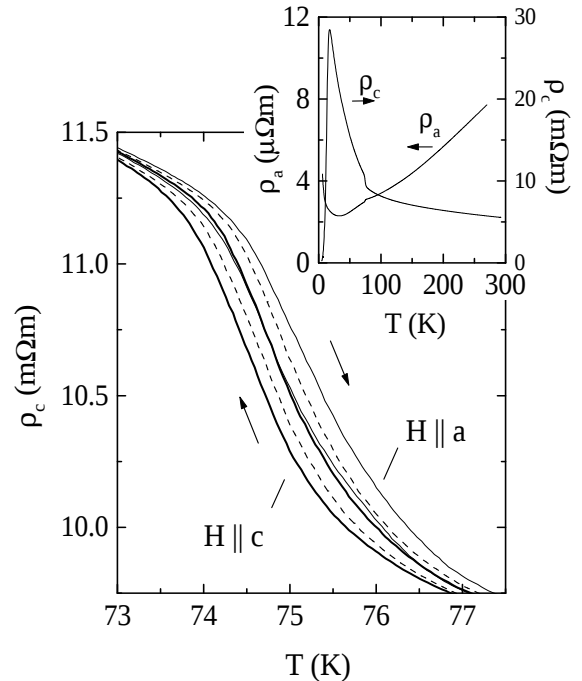


FIG. 1. (Main Panel) Hysteresis curves of ρ_c vs. T near T_d in $\text{La}_{2-y-x}\text{Nd}_y\text{Sr}_x\text{CuO}_4$ (Sample A1, with $x=0.10$). Curves are measured in zero field (broken lines), in a fixed 14-T field $\mathbf{H} \parallel \mathbf{c}$ (heavy solid lines), and in a 14-T field $\mathbf{H} \parallel \mathbf{a}$ (light solid lines). T_d is shifted down (up) if the field is parallel to the c -axis (a -axis). The inset shows the resistivities ρ_a and ρ_c in A1.

We confirmed these numbers by independent tests, and also checked that the sensitivity is unaffected by the field tilt-angle. At our largest field (14 T), the error in the set-point temperature is < 35 mK, and easily compensated for. The crystals were cut from boules grown in an image furnace. Samples A1 and A2 have the same Sr content,

$x = 0.10$, while Sample B has a higher x (0.15) (the Nd content $y = 0.6$ is the same in all samples).

II. FIELD EFFECT ON T_D

In zero field, the T dependences of ρ_a and ρ_c (Fig. 1, inset) are similar to those previously observed in crystals of $\text{La}_{2-y-x}\text{Nd}_y\text{Sr}_x\text{CuO}_4$ with $y = 0.4$ and $x = 0.12$ [5]. Whereas ρ_a is only slightly affected by the LTO-LTT transition, ρ_c increases steeply below T_d until 20 K, where a broad transition to superconductivity begins. As shown in Fig. 1 (main panel), ρ_c is hysteretic near T_d between warming and cooling, consistent with a first-order phase transition. In an applied field $\mathbf{H}$, the hysteresis loop is displaced down in T if $\mathbf{H} \parallel \mathbf{c}$, but is displaced up if $\mathbf{H} \parallel \mathbf{a}$ (the upward displacement is independent of the direction of $\mathbf{H}$ within the ab plane). This indicates a corresponding shift in the transition temperature T_d . The shift ΔT_d is nonlinear in B^2 . For $\mathbf{H} \parallel \mathbf{a}$, $\Delta T_d \sim +250$ mK at 14 T (it is negative and slightly smaller if $\mathbf{H} \parallel \mathbf{c}$).

In sample B (near optimal doping) the shift ΔT_d is also similar in magnitude. In Fig. 2, we show the displacements of the hysteresis loop for the in-plane resistivity ρ_a . The relatively large MR signal raises ρ_a overall by $\sim 0.4\%$ when the field is at 14 T. Nonetheless, the shifts in T_d (positive when $\mathbf{H} \parallel \mathbf{a}$ and negative $\mathbf{c}$) are quite apparent.

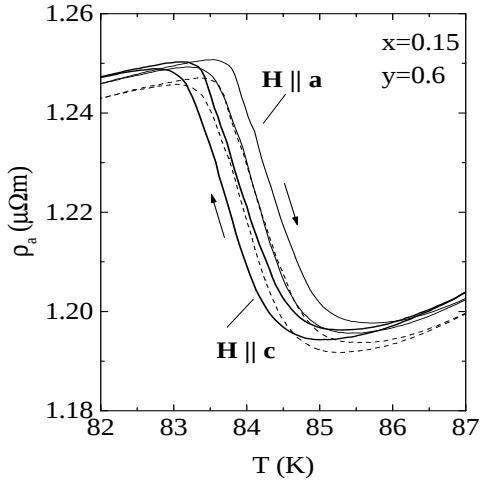


FIG. 2. Hysteresis curves of ρ_a vs. T in Sample B (with $y=0.6$, $x=0.15$) taken in zero field (broken lines), in a 14-T field $\mathbf{H} \parallel \mathbf{c}$ (heavy solid lines), and in a 14-T field $\mathbf{H} \parallel \mathbf{a}$ (light solid lines).

The unusual shift of T_d , together with the steep increase of ρ_c below T_d , leads to a large contribution to the MR observed at fixed temperature (in addition to the intrinsic MR response). The profile of ρ_c vs. T suggests that, in the vicinity of T_d , $\partial\rho_c/\partial T$ is most sensitive to $T - T_d$. Hence, we may write for the ‘weak-field’ regime (where $\Delta\rho_c \sim B^2$),

$$\left(\frac{\partial\rho_c}{\partial B^2}\right)_{obs} = \left(\frac{\partial\rho_c}{\partial B^2}\right)_{int} - \frac{\partial\rho_c}{\partial T} \frac{\partial T_d}{\partial B^2}. \quad (1)$$

The first and second terms on the right are the intrinsic and the T_d -shift terms, respectively. To demonstrate that both terms exist, we have measured the MR response in both field geometries (hereafter, we focus on Samples A1 and A2 in which $x=0.10$).

As dictated by the sign of $\partial T_d/\partial B^2$, the T_d term adds a spike to the MR signal that is negative for $\mathbf{H} \parallel \mathbf{c}$ and positive for $\mathbf{H} \parallel \mathbf{a}$.

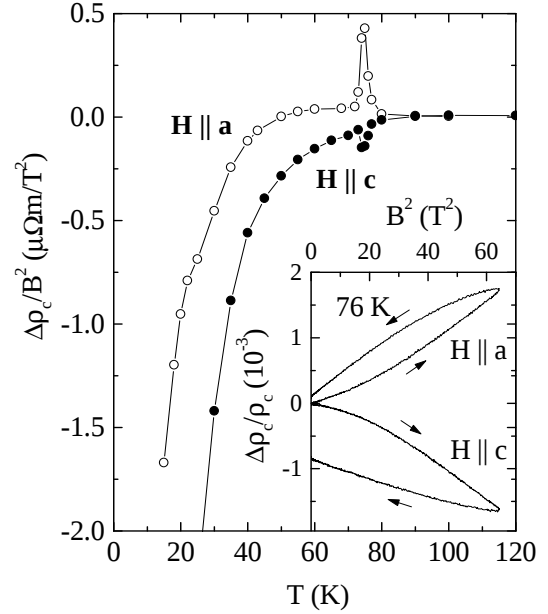


FIG. 3. (Main Panel) The MR signal $\Delta\rho_c$ (divided by B^2) versus T for $\mathbf{H} \parallel \mathbf{c}$ (solid circles) and $\mathbf{H} \parallel \mathbf{a}$ (open) (the latter changes sign near 40 K) in Sample A1. The MR is expressed as a fractional change in ρ_c at 1 Tesla. The spikes at T_d are caused by the T_d -shift contribution. The inset displays hystereses vs. H with T fixed at 76 K. With the sample prepared on the upper branch of the $\rho_c - T$ hysteresis loop at $H=0$, a large remanent $\Delta\rho_c$ is observed after field-cycling to 8 T and back to 0, if $\mathbf{H} \parallel \mathbf{c}$. The remanence is absent if $\mathbf{H} \parallel \mathbf{a}$ (see text).

This is confirmed by our measurements. The spikes in the MR curves taken at fixed T provide an independent check that T_d is shifted up (down) when $\mathbf{H} \parallel \mathbf{a}$ ($\mathbf{H} \parallel \mathbf{c}$).

Because ρ_c is hysteretic close to T_d (Fig. 1), it also displays strong hystereses when H is cycled in the vicinity of T_d . A detailed analysis shows that, with T fixed, increasing $\mathbf{H} \parallel \mathbf{a}$ is equivalent to decreasing the reduced temperature $\epsilon = (T - T_d)/T_d$ in zero field, whereas increasing $\mathbf{H} \parallel \mathbf{c}$ increases ϵ . We start with the system on the upper branch of the hysteretic loop in Fig. 1 at $H = 0$. If H is increased slowly along the c -axis, and then returned to zero, $\Delta\rho_c$ displays a large negative ‘remanence’ (Fig. 3, inset). If instead, $\mathbf{H}$ is applied $\parallel \mathbf{a}$, the field cycling leads to zero remanence (the opposite is true on the lower branch). For the two field geometries,

the distinctive correlation between the remanence (finite or zero) and the starting branch agrees well with predictions based on the execution of minor hysteresis loops as ϵ is cycled in zero field. It lends further support to the shift in T_d with field. The MR signals in the spike region shown in the main panel of Fig. 3 correspond to the initial $\Delta\rho_c$ with the system in the lower (upper) branch for $\mathbf{H} \parallel \mathbf{a}$ ($\mathbf{H} \parallel \mathbf{c}$).

III. 1D ANTIFERROMAGNETS

In magnetic systems, a shift in the ordering temperature that changes sign with field direction is quite rare. [In 3D antiferromagnets (AF), the applied field invariably leads to a decrease in the Néel temperature T_N [12].] The only previously known case appears to be quasi-one-dimensional (1D) antiferromagnetic systems, such as $\text{CsMnCl}_3 \cdot 2\text{H}_2\text{O}$ and CsNiCl_3 [14,15,13]. These materials are well-described as 1D Heisenberg antiferromagnets that become 3D-ordered at low T ($T_N \sim 5\text{K}$) because of a weak interchain coupling. A field parallel to the easy axis ($\mathbf{b}$) depresses T_N whereas a field perpendicular to $\mathbf{b}$ increases T_N . Calculations [16] show that, in a classical 1D antiferromagnet at low T , a magnetic field leads to an increase in the staggered susceptibility $\chi_\perp(q)$ with $q = \pi$. Villain and Loveluck (VL) [17] interpret the enhancement in terms of the correlation length ξ along the chain.

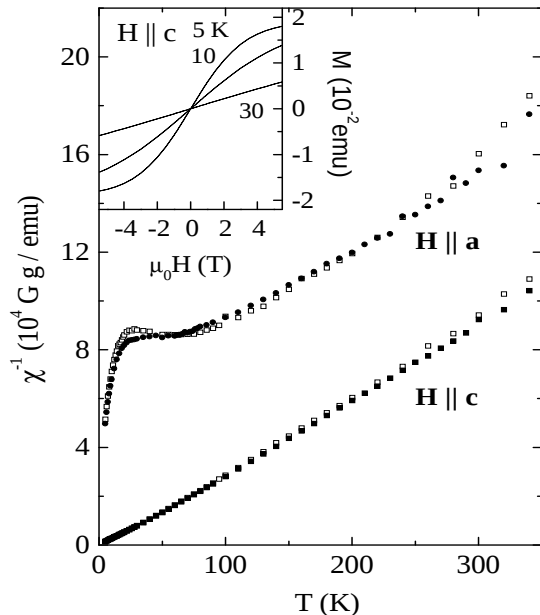


FIG. 4. The T dependence of the inverse susceptibility χ^{-1} at 1 Tesla for $\mathbf{H} \parallel \mathbf{a}$ and $\parallel \mathbf{c}$ in Samples A1 (open) and A2 (closed symbols). The inset shows the magnetization M vs. $\mathbf{H} \parallel \mathbf{c}$ at low T in 2. The $M-H$ curve for the a -axis geometry is nearly linear even at 5 K.

Suppression of magnetic fluctuations along the field direction has the effect of reducing by one the number of

spin components (from Heisenberg to XY , for instance). This implies an increase in ξ , which in turn enhances T_N . Fits using these calculations account well for the H dependence of T_N observed in several compounds [13]. Before applying these ideas to our samples, we discuss the susceptibility measurements.

IV. SUSCEPTIBILITY

The uniform susceptibility χ in our samples was measured in a 1-Tesla field using a SQUID magnetometer. Figure 4 compares the T dependence of χ_a^{-1} and χ_c^{-1} obtained with $\mathbf{H} \parallel \mathbf{a}$ and $\mathbf{H} \parallel \mathbf{c}$, respectively. For $\mathbf{H} \parallel \mathbf{c}$, χ_c^{-1} is Curie-like, except that the high- T straight-line extrapolations show intercepts of 4.9 (8.5) K in Sample A1 (A2). The slope of χ_c^{-1} yields a large effective moment per Nd ion, $p_{eff} = 5.1$ (5.3) μ_B (Bohr magneton). Our χ_c is qualitatively similar to the susceptibility in an earlier report [2] for χ measured with $\mathbf{H}$ along an unspecified direction. As shown in the inset, the magnetization M vs. $\mathbf{H} \parallel \mathbf{c}$ is linear above 10 K, but shows incipient ferromagnetic behavior below. The rapid increase in ordering of the Nd moments below 3 K has been detected by neutron scattering [2]. The large magnitude of p_{eff} and the apparent ferromagnetic ordering imply that the uniform susceptibility is dominated by the Nd spins $\mathbf{S}$. Surprisingly, the in-plane susceptibility χ_a is qualitatively different in behavior. Above 100 K, it is consistent with Curie-Weiss behavior $\chi_a \sim 1/(T + \theta)$ with $\theta \sim 180$ K. Below T_d , χ_a^{-1} displays a levelling off that is reminiscent of the response of an antiferromagnet.

The nearly Curie-like behavior of χ_c implies that the c -axis components of the Nd spins S_z behave as free spins right through T_d (we take $\hat{\mathbf{z}} \parallel \mathbf{c}$). However, the profile of χ_a shows that the in-plane components S_x and S_y undergo ordering at T_d . The measurements suggest that S_x and S_y are strongly coupled to the Cu spins as well as to the phonon mode associated with the tilting of the octahedra, but S_z is not. Hence, fluctuations of S_x and S_y strongly influence magnetic ordering of the Cu spins and the lattice distortion, whereas fluctuations in S_z do not.

An attractive picture is that the rapid growth of the staggered susceptibility $\chi_{xx}(\mathbf{Q})$ is presumably responsible for the LTO-LTT transition [$\mathbf{Q} = (\pi, \pi)$, nominally]. As in the model of Villain and Loveluck [17], an external field selectively suppresses fluctuations along the field axis. When $\mathbf{H} \parallel \mathbf{x}$ or $\mathbf{y}$, this suppression enhances $\chi_{xx}(\mathbf{Q})$ (and hence T_d). However, a field $\parallel \mathbf{c}$ is ineffective because fluctuations along $\mathbf{c}$ are irrelevant to the transition at T_d . This picture may allow us to relate the unusual anisotropy of the susceptibility to the striking shift of T_d by an applied field. It also emphasizes our key finding that the LTO-LTT transition is intrinsically magnetic in nature.

V. IN-PLANE MAGNETORESISTANCE

The anisotropic nature of the magnetic susceptibility also has striking consequences for conductance in the plane. We have measured the in-plane magnetoresistance (current $\mathbf{J} \parallel \mathbf{a}$) in Sample A2 for both $\mathbf{H} \parallel \mathbf{c}$ and $\mathbf{H} \parallel \mathbf{a}$ (Fig. 5). Unlike the c -axis MR, the in-plane MR is always positive. Above T_d , the in-plane MR is virtually identical in magnitude for the two field directions, whereas, below T_d , the MR signal is slightly weaker (by ~ 2) when $\mathbf{H} \parallel \mathbf{a}$.

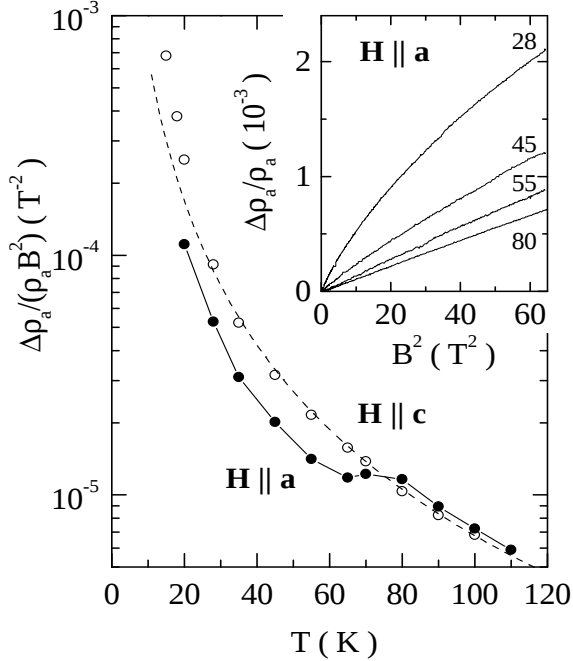


FIG. 5. The MR signal for the (weak-field) in-plane resistivity ρ_a expressed as the fractional change in ρ_a divided by B^2 (sample A2). A slight anomaly is observed in the curve for $\mathbf{H} \parallel \mathbf{a}$, but not for $\mathbf{H} \parallel \mathbf{c}$. The broken line is a T^2 fit to the data for $\mathbf{H} \parallel \mathbf{c}$. The inset shows that the increase in ρ_a deviates from B^2 below 80 K.

The relatively large MR response (compared with Nd-free LSCO) and its isotropic nature above T_d imply that it arises entirely from the coupling of $\mathbf{H}$ to the spin degrees of the carriers (as well as to the Nd ions). Significantly, the MR curve for $\mathbf{H} \parallel \mathbf{c}$ passes through T_d without deflection, whereas the curve for $\mathbf{H} \parallel \mathbf{a}$ displays a broad anomaly at T_d . The selective sensitivity to the transition at T_d is consistent with that observed in χ . The MR data suggest that the stiffening below T_d of the spin response to a uniform in-plane field also leads to a decrease in the MR response for the same field direction. In contrast, the transition has no effect on χ or the MR when $\mathbf{H} \parallel \mathbf{c}$. Together, the two experiments reveal rather clearly how spin ordering also influences in-plane charge transport. A better understanding of how the MR arises may illuminate charge transport in the cuprates. We note that the positive sign is opposite to that in conventional

spin-mediated MR which predicts negative MR (the only mechanism that gives a positive MR seems to be from interaction theory [18]).

In summary, we have described 3 experiments that reveal the magnetic nature of the LTO-LTT transition in the striped cuprate Nd-doped LSCO. T_d is shifted up (down) when the applied field is in-plane (along the c -axis). The uniform susceptibility measured with $\mathbf{H} \parallel \mathbf{a}$ shows behavior consistent with AF ordering, but betrays no sign of the transition when measured with $\mathbf{H} \parallel \mathbf{c}$. The same sensitivity to field orientation is also apparent in the in-plane MR. The findings all point to a selective dependence of the LTO-LTT transition to field direction. We propose that field-suppression of spin fluctuations along the field axis plays a role similar to that in 1D Heisenberg systems. However, the many transport features of the striped phase, such as the influence of spin ordering on the resistivity, remain to be understood.

Discussions with G. Baskaran, D. Huse, B. Keimer, P.A. Lee, and J. Tranquada are acknowledged. We are especially indebted to B. Keimer for bringing to our attention the 1D spin-chain results. The work in Princeton is supported by a MRSEC grant (DMR 98-09483) from the U.S. National Science Foundation. N.P.O. and S.U. gratefully acknowledge support from International Joint-Research grants from the New Energy and Industrial Tech. Develop. Org. (NEDO), Japan.

*Permanent address of Z.A.X. Department of Physics, Zhejiang University, Hangzhou 310027, China.

- [1] J.M. Tranquada, B.J. Sternlieb, J. D. Axe, Y. Nakamura, and S. Uchida, *Nature* **375**, 561 (1995).
- [2] J. M. Tranquada *et al.*, *Phys. Rev. B* **54**, 7489 (1996).
- [3] M.v. Zimmermann *et al.*, *Europhys. Lett.* **41**, 629 (1998).
- [4] T. Niemöller *et al.*, *cond-mat/9904383*.
- [5] Y. Nakamura and S. Uchida, *Phys. Rev. B* **46**, 5841 (1992).
- [6] S. Uchida *et al.*, in *Physics and Chemistry of Transition Metal Oxides*, ed. H. Fukuyama and N. Nagaosa, (Springer-Verlag, Heidelberg) 1999, p. 163.
- [7] K. Yamada *et al.* *Phys. Rev. B* **57**, 6165 (1998).
- [8] A.W. Hunt, P. M. Singer, K. R. Thurber, and T. Imai, *Phys. Rev. Lett.* **82**, 4300 (1999).
- [9] P. M. Singer, A. W. Hunt, and T. Imai, *cond-mat/9906140*.
- [10] V. J. Emery and S. A. Kivelson, *Physica C* **209**, 597 (1993), S. A. Kivelson and V. J. Emery, *Strongly Correlated Electronic Materials: The Los Alamos Symposium 1993* edited by K.S. Bedell *et al.* (Addison Wesley, reading, MA), 1994, p. 619.
- [11] J. M. Harris *et al.*, *Phys. Rev. Lett.* **75**, 1391 (1995).
- [12] T. Nagamiya, K. Yosida, and R. Kubo, *Adv. in Phys.* **4**, 1 (1955).

- [13] W.J.M. de Jonge, J.P.A. Hijmans, F. Boersma, J.C. Schouten, and K. Kopinga, Phys. Rev. B **17**, 2922 (1978).
- [14] G. J. Butterworth and J. A. Woollam, Phys. Lett. **29A**, 259 (1969).
- [15] D.P. Almond and J. A. Rayne, Phys. Lett. **55A**, 137 (1975).
- [16] M. Blume, P. Heller, N.A. Lurie, Phys. Rev. B **11**, 4483 (1975); S. W. Lovesey and J. M. Loveluck, J. Phys. C **9**, 3639 (1976).
- [17] J. Villain and J. M. Loveluck, J. de Phys. (Paris) Lett. **38**, L-77 (1977).
- [18] For a review, see P.A. Lee and T. V. Ramakrishnan, Rev. Mod. Phys. **57**, 286 (1985).